arXiv:cond-mat/9901207v2 [cond-mat.str-el] 27 Jan 2000

Resistive Anomalies at Ferromagnetic Transitions Revisited: the case of SrRuO$_3$

R. Roussev and A. J. Millis
Center for Materials Theory and Department of Physics and Astronomy, Rutgers University, 136 Frelinghuysen Road, Piscataway NJ 08854-8019

It is generally believed [1,2] that near a ferromagnetic phase transition the resistivity, ρ, exhibits an energy-like singularity so $\mathrm{d}\rho/\mathrm{d}T \sim |t|^{-\alpha}$ with $\alpha \approx 0.1$ the specific heat exponent and $t = (T - T_c)/T_c$. In a recent Letter [3], Klein *et al.* claimed that in SrRuO$_3$, a strongly correlated "bad metal", the resistive anomaly at T_c is anomalous: at $T > T_c$, $\mathrm{d}\rho/\mathrm{d}T \sim t^{-x}$ with $x \approx 0.9$ while for $T < T_c$ $\mathrm{d}\rho/\mathrm{d}T$ cannot be fit by any power law. Klein *et al.* obtained exponents by plotting $\ln|\mathrm{d}\rho/\mathrm{d}T - S_0|$ vs $\ln T/T_c$ (S_0 is a T-independent background), a procedure shown to be unreliable in many cases [5,7].

We show here that the data are consistent with conventional theory, [1,2] which predicts

$$\mathrm{d}\rho/\mathrm{d}T = (A_\pm/\alpha)|t|^{-\alpha}(1 + D_\pm|t|^\theta) + S(t), \qquad (1)$$

where $A_\pm$ and $D_\pm$ are the amplitudes for the leading singularity and correction to scaling, α and θ are the specific heat and correction to scaling exponents and $+(-)$ refer to $t > 0 (t < 0)$. $S(t)$ is a smooth function of t which we approximate by $S(t) = S_0 + S_1 t$. Eq. (1) applies within a critical region $|t| < t_{\mathrm{crit}}$. The fits to χ in [3] imply $t_{\mathrm{crit}} \sim 0.13$; fitting $|t| > t_{\mathrm{crit}}$ requires a crossover theory [7]. Due to rounding of the data very near T_c points with $|t| < t_{\mathrm{round}}$ have been excluded. Following [4] we allowed for 1% variations in T_c about the nominal value $T_c^* = 150$K. The fits depend crucially on t_{crit}, t_{round} and t_c. Fig. 1 shows the data along with fits to Eq. (1) using Heisenberg exponents $\alpha_H = -0.1$ and $\theta_H = 0.55$, and universal amplitude ratios $(A_+/A_-)_H = 1.52$ and $(D_+/D_-)_H = 1.4$ [6] with and without corrections to scaling for $t_{\mathrm{round}} = 0.01$ and parameters given in Table I. Using Ising parameters in Eq. (1) produces slightly worse fits (not shown). The curve *with* corrections to scaling (i.e. $D_+ \neq 0$) and $t_{\mathrm{crit}} = 0.1$ is our best fit with accepted universal amplitude ratios; varying these gives exact fits over the range $t \in (-0.2, 0.5)$. The results of [3] imply that the $t > 0$ behavior is also consistent with $\alpha \approx 0.9$, but we believe the consistency with conventional theory renders alternative interpretations implausible.

One of us [8] had previously suggested that in systems with very strong carrier-spin interactions, a term in $\rho(T)$ proportional to the square of the magnetization, $\mathcal{M}^2$, could arise at $T < T_c$. This suggestion was based on an erroneous interpretation of a spherical model calculation and is here withdrawn. Briefly, any scattering process contributing to ρ involves a combination of spin operators at nearby points [1] and in a ferromagnet these can only involve the specific heat exponent. In the spherical model the specific heat and $\mathrm{d}\mathcal{M}^2/\mathrm{d}T$ have identical behavior.

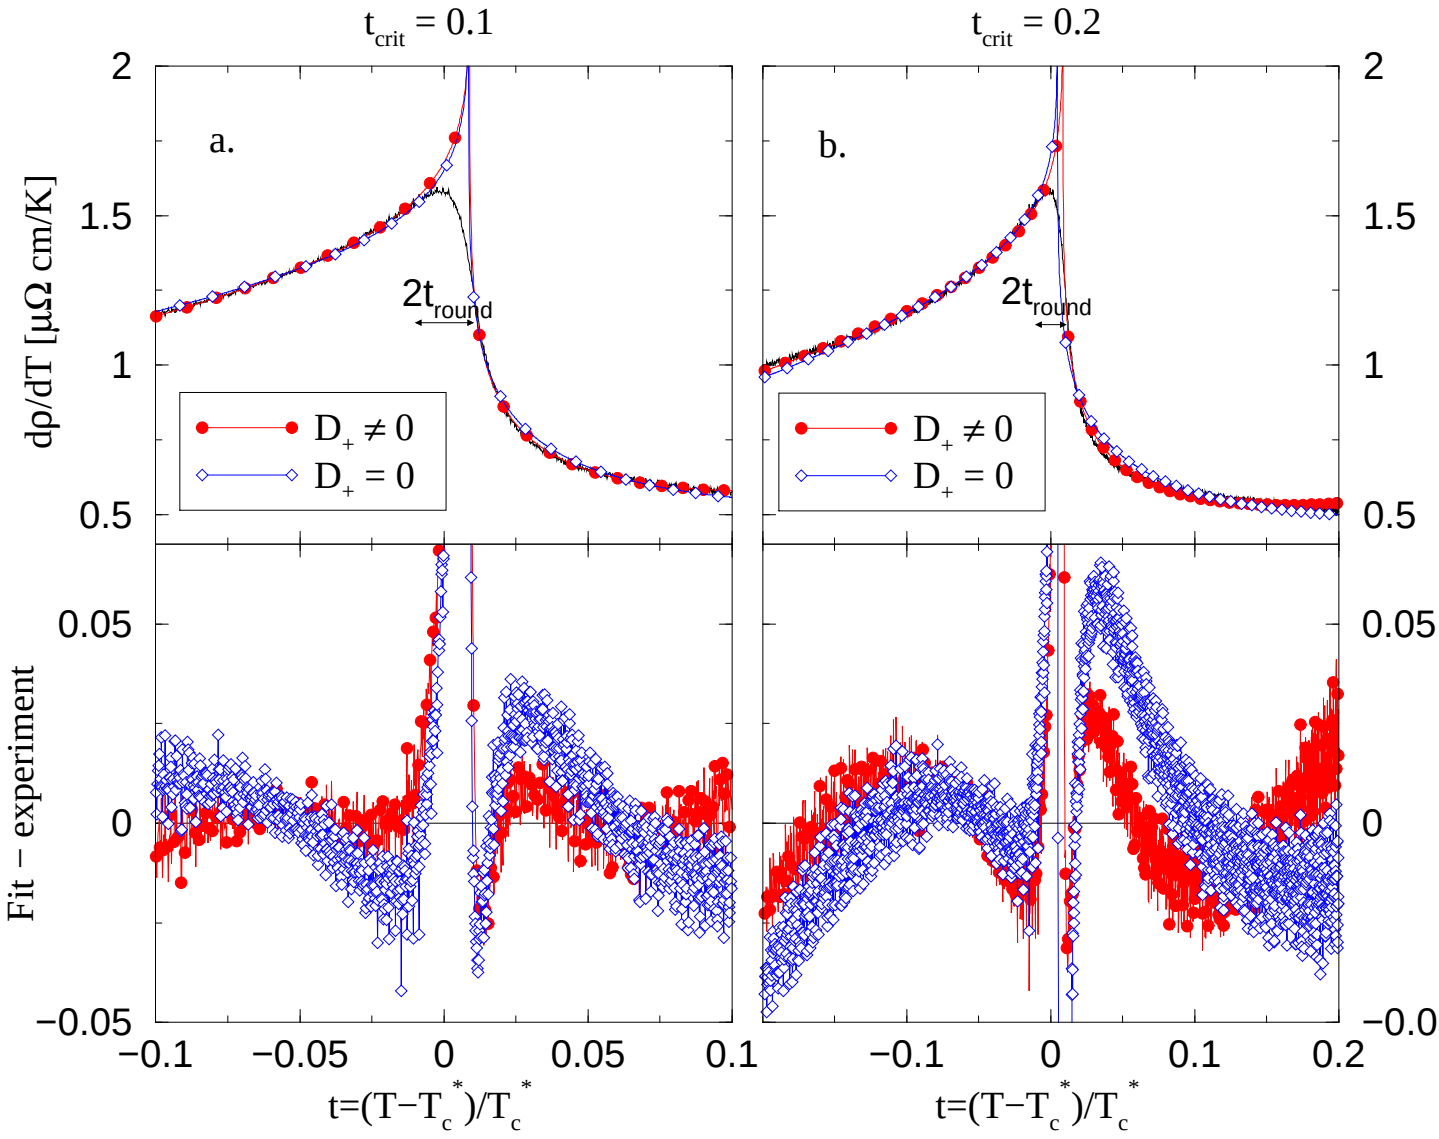

FIG. 1. Experimental data [3] and Heisenberg fits with Eq. (1) (upper graphs) for $t_{\mathrm{round}} = 0.01$. The lower graphs show the difference between Eq. (1) and the data. $T_c^* = 150$ K.

We thank L. Klein for data, M. E. Fisher, J. Ye and J. S. Dodge for helpful conversations, J. S. Dodge for pointing out an error in our previous analysis, and NSF - DMR - 9707701 and the Johns Hopkins MRSEC.

t_{crit}	0.1	0.1	0.2	0.2
A_+	0.3820	0.3331	0.3484	0.3052
D_+	-0.256	0.0	-0.171	0.0
S_0	3.238	3.043	3.071	2.886
S_1	1.556	1.316	1.126	1.052
t_c	-0.0090	-0.0070	-0.0086	-0.0048

TABLE I. Fitting parameters for Eq. (1) with $t \to t + t_c$.

---

[1] M. E. Fisher, J. S. Langer, Phys. Rev. Lett. **20**, 665 (1968).
[2] S. Alexander *et al.*, Phys. Rev. B **13**, 304 (1976).
[3] L. Klein *et al.*, Phys. Rev. Lett. **77**, 2774 (1996).
[4] A. Kornblit and G. Ahlers, Phys. Rev. B **11**, 2678 (1975).
[5] See, e.g. p. 2 of G. Ahlers in *Phase Transitions, Cargese 1980*, M. Levy *et. al.* eds, (Plenum, New York, 1982) or sec. V of M. E. Fisher, Rev. Mod. Phys. **46**, 597 (1974).

[6] V. Privman *et al.*, v. 14 of *Phase Transitions and Critical Phenomena*, eds C. Domb and J. Lebowitz (Academic, New York, 1991).
[7] Z. Y. Chen *et al.*, Phys. Rev. A **41**, 3161 (1990).
[8] A. J. Millis *et al.*, Phys. Rev. Lett. **75**, 5144 (1995).